

STELCAR™ JET KOTE™ 112

TECHNICAL DATA

| HVOF & PLASMA SPRAY DEPOSITION |

PREMIUM QUALITY HVOF COATING

JK™ 112 powder is manufactured by the agglomeration, sintering and densification of fine particles of tungsten carbide and cobalt. **JK™ 112** is similar in composition to Praxair D-Gun® LW-1N30 coatings. Highly polished surface finishes are possible because of the fine size and homogeneous distribution of the WC particles.



TYPICAL APPLICATIONS

JK™ 112 has excellent resistance to abrasion, low angle erosion and sliding wear. The extremely high abrasion resistance is associated with lower toughness when compared to **JK™ 117** or **JK™ 120H**, both of which contain a higher proportion of metallic binder. **JK™ 112** outperforms hard chrome plating in most wear situations, and is often used as a hard chrome substitute. It is especially recommended for applications where a fine coating surface finish is a major requirement. **JK™ 112** is used for the coating of compressor rods, pump casings, pump plungers, pump sleeves, mechanical seal faces, feed screws, gate valves, valve trim, thread guides, paper cutting and slitter knives and fan blades. It is also used for various chemical and petrochemical parts.

SLIDING WEAR RESISTANCE OF JK™ 112 HVOF COATINGS

In a cross cylinder wear test, where a 0.5" (12.7mm) diameter WC-6%Co cutter blank slid against the coating surface with a 15lb (6.8kg) load for one hour, the **JK™ 112** HVOF coating exhibited no measurable wear. A nitrided surface in the same test lost 0.7 mm³ material, chrome plating lost 1.6 mm³.

ABRASION WEAR RESISTANCE TEST RESULTS

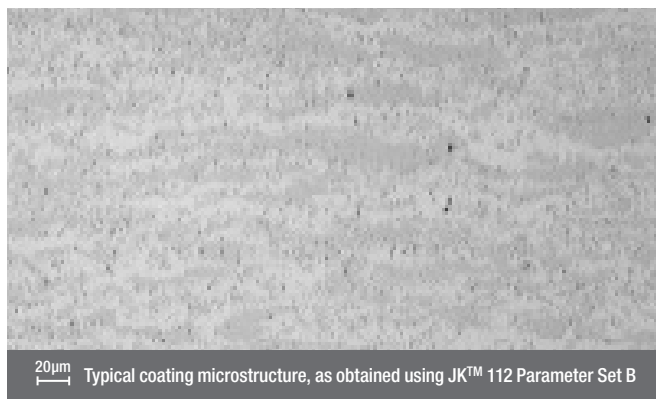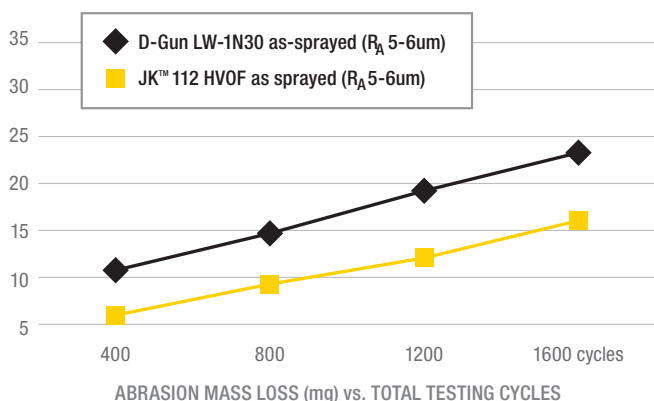

SUPERIOR ABRASION WEAR RESISTANCE OF JK™ 112 HVOF COATINGS

The mass loss (mg) of **JK™ 112** vs. Praxair D-Gun® LW-1N30 coatings was measured in an independent abrasion test¹ conducted according to JIS H8615. The coatings were abraded by 320 grit SiC paper at an applied load of 3.25kg. The results are illustrated schematically at bottom left, and indicate that the mass loss of **JK™ 112** is only 60–70% that of D-Gun® LW-1N30, reflecting the superior abrasion resistance of **JK™ 112**.

When both coatings were tested after surface finishing to R_A ~ 0.2µm, the mass loss of both coatings was much lower, of the order of 2 mg for **JK™ 112** and 4.5 mg for D-Gun® LW-1N30 after 1600 cycles. After 4000 cycles in the same test, a polished **JK™ 112** coating (R_A ~ 0.2 µm) exhibited a mass loss of below 5 mg. Hard chrome had a mass loss greater than 26 mg, over five times higher than **JK™ 112**.

CORROSION RESISTANCE OF JK™ 112 COATINGS

JK™ 112 has acceptable corrosion resistance in a number of environments, especially if sealed. As for all coatings, if the substrate is not resistant to the environment the coating should

1. Results published courtesy of Tocalo Ltd., Japan, <http://www.tocalo.co.jp>



www.kennametal.com/stellite

be sealed, especially at the edges of the coating and base material. The potential for cobalt to leach out in aqueous conditions, due to crevice or galvanic corrosion, can significantly reduce the usable life of JK™ 112 coatings in certain service conditions. JK™ 112 is not recommended with solutions containing amines. JK™ 120H WC-Co-Cr is recommended for applications where corrosion resistance is a primary requirement.

COATING PROPERTIES

	Set A (propylene fuel)	Set B (propylene fuel)
Microhardness	960–1150 DPH [300g]	1015–1120 DPH [300g]
Macrohardness	90–91 R15N (equivalent to 66HRC)	89–93 R15N (equivalent to 66–68HRC)
Bond Strength (ASTM C633)	>75.9 MPa (>11 ksi)	>75.9 MPa (>11 ksi)
Est. Porosity	<1.5 %	<1.0 %
Density (approx.)	12.5 g/cm ³	>13 g/cm ³
Max. Coating Thickness	0.38 mm (0.015")	0.25 mm (0.010")
Max. Coating Thickness		0.38 mm (0.015")
D.E. Approx.	58%	53%
Powder Feed	50–60 g/min.	50–60 g/min.
Coverage (Estimated)	325 g.m. ⁻² 100µm ⁻¹ (1.7 lb.ft. ⁻² 0.1in ⁻¹)	345 g.m. ⁻² 100µm ⁻¹ (1.8 lb.ft. ⁻² 0.1in ⁻¹)
Surface Finish (As-sprayed AA)	4.7–7.6 µm (185–300 µ-inch)	3.8–6.3 µm (150–250 µ-inch)
Surface Finish (Ground/Lapped)	<0.025–0.05 µm (below 1–2 µ-in.) AA	
Service Temp.	Up to approx. 540°C (1000°F)	

SPRAYING OF JK™ 112 HVOF COATINGS

Although the use of the Jet Kote™ HVOF system with a carbon based fuel such as propylene is recommended, JK™ 112 powder can also be deposited using other HVOF systems. JK™ 112H is recommended for systems using hydrogen as main fuel.

NOMINAL POWDER PROPERTIES

Mass Composition:	88%WC 12%Co
Nominal Size:	–53+10µm (–270 mesh+10µm)
Production Method:	Agglomerated, sintered and densified

CUSTOMER SPECIFICATIONS

JK™ 112 powder and/or coating are similar to BPS 4463, B50TF27 CL.B, F50TF80 CL.B, EMS 57736 Type 2, EMS 52544 Type 2, AMS 7880, RR9507/58, Mil-P-83348 Comp J Type II CL.I, BAC 5851, and ISO 14232 Code 11.12.

SIMILAR POWDER PRODUCTS

- Kennametal Stellite GmbH JK™ 7112
- Sulzer Metco™ 72F
- Diamalloy™ 2004
- Amperit™ 518
- AMDRY™ 927
- Sulzer Metco™ 5812
- TAFE Praxair 1342VM

FINISHING OF JK™ 112 HVOF COATINGS

JK™ 112 coatings are typically finished to 6–14 µ-inches by wet diamond grinding. They can be super finished using diamond-lapping compound to below 1–2 µ-inch (0.025–0.050µm) if required. Coolant must be flooded onto part and wheel during grinding. The coolant may not contain Amines, which can attack and pit the cobalt matrix.

SPRAYING AND GRINDING/FINISHING PARAMETERS FOR JK™ 112 ARE AVAILABLE ON REQUEST.

JP-5000 is a trademark of Praxair-TAFA Inc. D-Gun is a trademark of Praxair Inc. Amperit is a trademark of H.C. Starck. Diamalloy and AMDRY are trademarks of SULZER METCO Inc.

Kennametal Stellite™ manufactures sophisticated alloys in the form of castings, powders, coatings, consumables, and machined parts that resist wear, corrosion, and abrasion. Information provided in this document is intended only for general guidance about Kennametal Stellite™ products and is the best information in our possession at the time. Product users may request information about their individual use of our products, but Kennametal Stellite™ does not warrant or guarantee this information in any way. Selection and purchase of Kennametal Stellite™ products is the sole responsibility of the product user based on the suitability of each use. Individual applications must be fully evaluated by the user, including compliance with applicable laws, regulations, and non-infringement. Kennametal Stellite™ cannot know or anticipate the many variables that affect individual product use and individual performance results may vary. For these reasons, Kennametal Stellite™ does not warrant or guarantee advice or information in this document, assumes no liability regarding the same, and expressly disclaims any warranty of any kind, including any warranty of fitness for a particular purpose, regarding the same.

EUROPEAN SALES OFFICES

Kennametal Stellite Unit 3, Birch Kembrey Business Park Swindon SN2 8UU UK Phone: 44.1793.498500 Fax: 44.1793.498501	Kennametal Stellite Zur Bergpflege 51 – 53 56070 Koblenz Germany Phone: 49.261.80.88.0 Fax: 49.261.80.88.35	Kennametal Stellite Via G. Di Vittorio, 24 20090 Pieve Emanuele Milan Italy Phone: 39.02.907871 Fax: 39.02.90787 231
---	---	---

E-mail: europesales.stellite@kennametal.com

AMERICAS SALES OFFICE

Kennametal Stellite
1201 Eisenhower Drive N
Goshen, Indiana 46526
USA
Phone: 1.574.534.2585
Fax: 1.574.534.3417

E-mail: americasales.stellite@kennametal.com



www.kennametal.com/stellite